

RESEARCH PAPER

Efficiency of Chitosan-Grafted Poly (Carboxymethyl Cellulose-Co-Acrylamide) Nano Hydrogel for Cadmium (II) Removal: Batch Adsorption Study

Qusay K. Mojar Alshamusi ¹, Khitam Abdul Ameer Hameed ², Ali M. Taher ³, Maryam Batool ⁴, and Layth S. Jasim ^{1*}

¹ Department of Chemistry, College of Education, University of Al-Qadisiyah, Al-Qadisiyah, Iraq

² Ministry of Education, General Directorate of Babylon Education, Iraq

³ Department of Chemistry, College of Science, University of Al-Qadisiyah, Diwaniya 1753, Iraq

⁴ Department of Chemistry, University of Sahiwal, Sahiwal, Pakistan

ARTICLE INFO

Article History:

Received 9 April July 2024

Accepted 01 May 2024

Published 01 October 2024

Keywords:

CS-g-P(CMC-co-AM) nano hydrogel

Cadmium (Cd) ions

Batch adsorption

Kinetics

ABSTRACT

Presence of heavy metals (HMs) mainly cadmium (Cd (II)) ions in water cause serious environmental and health risks that needs to be addressed by some effective method. Current study involved the use of Chitosan-grafted Poly (Carboxymethyl Cellulose-Co-Acrylamide) Nano Hydrogel for Cd (II) ions removal from water. The prepared nano hydrogel was characterized via Fourier Transform Infrared (FTIR) spectroscopy, Field Emission Scanning Electron Microscopy (FESEM) and X-ray Diffraction (XRD). The results of these techniques revealed the presence of different types of functional groups in nano hydrogel structure that possess highly rough and amorphous texture. Adsorption study was conducted for investigating the effects of contact time, solution pH, nano hydrogel dose, and ionic strength of different salts (NaCl, KCl, CaCl₂) on Cd (II) removal. Findings of the study highlights maximum removal of 93.3% with adsorption capacity 37.3 mg/g in 90 minutes while using 200 mg/L Cd (II) solution of pH 10. Kinetic study showed fitness of adsorption process with pseudo second model with regression coefficient value equal to unity signifying a chemical adsorption mechanism. Overall, the prepared CS-g-P(CMC-co-AM) nano hydrogel possess adsorption potential for cadmium ions removal from water.

How to cite this article

Alshamusi Q., Hameed K., Taher A., Batool M., Jasim L. Efficiency of Chitosan-Grafted Poly (Carboxymethyl Cellulose-Co-Acrylamide) Nano Hydrogel for Cadmium (II) Removal: Batch Adsorption Study. J Nanostruct, 2024; 14(4):1122-1133. DOI: 10.22052/JNS.2024.04.013

INTRODUCTION

The extensive use of heavy metals (HMs) in modern world led to their increased levels in water sources resulting in deteriorating water quality and affecting all life forms on earth. Cadmium (Cd) is one of the toxic metals that enter water system via variety of routes such as galvanized pipes and

metal fittings. When ingested, Cd is responsible for causing human organ dysfunction. Keeping in view the toxicity caused by Cd, Department of Environment, UK and European Economic Community placed this metal in red list of priority contaminants and black list of Dangerous Substance Directive respectively [1]. Researchers

* Corresponding Author Email: layth.alhayder@gmail.com



This work is licensed under the Creative Commons Attribution 4.0 International License.

To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

are now working on the development of effective and low-cost methods for removal of Cd (II) ions from water. Several physio-chemical and biological methods [2, 3] have been developed aiming to treat polluted water. However, high operational cost and secondary pollution associated with them make them ineffective for treating all kinds of pollutants in water [4-19]. Adsorption, however, an effective and efficient technique for water treatment takes precedence over all other conventional methods due to its simple design, low cost and easy availability of adsorbents.

In adsorption method, selection of adsorbents for efficient pollutant removal is a crucial step. Various kinds of natural and synthetic adsorbents have been developed and used till date for Cd (II) adsorption [1, 20-29]. This study, however, investigated the adsorptive removal of Cd (II) ions from water using poly (carboxymethyl cellulose-co-acrylamide) (CS-g-P(CMC-co-AM)) nano hydrogel as an adsorbent. The nano hydrogel was characterized by FTIR, FESEM, and XRD techniques. Swelling properties of prepared nano hydrogels were also investigated under variable pH of solution. Influence of adsorption factors as contact time, pH, adsorbent dosage, salt concentration was also studied. The nature of adsorption process was investigated by applying the time data on two different kinetic models namely pseudo first and pseudo second order kinetic models.

MATERIALS AND METHODS

Materials and chemicals used

The experimental reagents used in study were acrylamide (AM), chitosan, hydrochloric acid, Carboxymethyl cellulose sodium salt (CMC), ethanol, potassium persulfate, bis-acrylamide, acrylic acid, nitrogen gas, acetic acid,

tetramethylethylenediamine (TMEDA), sodium chloride, potassium chloride, and calcium chloride. These chemicals were essential components in conducting batch adsorption experiments and analyzing the results.

Preparation of Cd (II) solution

A stock solution (500 mg/L) of cadmium (II) ions was prepared by dissolving 1.37 grams of cadmium nitrate tetrahydrate ($\text{Cd}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$) in distilled water. The solution was quantitatively transferred to volumetric flask (1000 mL) and diluted to final volume by addition of water. Working solutions of variable concentrations were subsequently prepared from this stock solution for further experimentation.

Synthesis and characterization of nano hydrogel CS-g-P(CMC-co-AM)

The prepared nano hydrogel i.e., CS-g-P(CMC-co-AM) was synthesized via preparation of two different solutions [30, 31]. Firstly, solution 1 was prepared a 1% of acetic acid (AAC), dissolve 0.5 g of chitosan (CS) in 20 mL of this solution and dissolving 6g acrylamide in 10 mL deionized water which was then combined with solution of acrylamide (6g in 10 mL water). A solution of N, N'-methylenebisacrylamide (MBA) was prepared by dissolving its 0.05g in 5 mL deionized water. This solution was then added to mixture and stirred for 15 min with simultaneous introduction of nitrogen gas. Followed by preparation of solution 1, next step is to prepare solution 2. For this, 0.5 g Carboxymethyl cellulose sodium salt was dissolved in 10 mL deionized water that was stirred continuously for 15 min. Afterwards, potassium persulfate (KPS) solution (0.1g in 5 mL water) and a TEMED solution (0.05g in 5 mL water) were



Fig. 1. Prepared CS-g-P(CMC-co-AM) nano hydrogel.

added to above mixture serially with continuous stirring. This was followed by addition of Solution 1 (in a dropwise manner) to Solution 2 at 50 °C while nitrogen gas was intermittently introduced for 30 sec. incubation of mixture was then carried out in a water bath at 60 °C for 2 hours that aid in completion of reaction. Obtained hydrogel was cut into smaller pieces that were then washed with water for one hour and oven-drying was done at 50 °C. The dried hydrogel was then ground into very fine particles having diameters varying from 50 to 250 nm. Fig. 1 shows prepared CS-g-P(CMC-co-AM) hydrogel.

The successful synthesis of nano hydrogel was confirmed by Fourier Transform Infrared (FTIR) spectroscopy (Shimadzu 8400s spectrophotometer within range of 500 to 4000 cm⁻¹), Field Emission Scanning Electron Microscopy (FESEM) (TESCAN MIRA3 at 25 kV) and X-ray Diffraction (XRD) analysis (Shimadzu XRD-6000, within 2θ range of 10° to 80°) that helps in analysis of functional groups [2, 32, 33] surface morphology [34, 35] and crystallinity of adsorbent [36] respectively.

Adsorption experiments

Batch adsorption study was carried out for investigating the effect of equilibrium time (0 min to 220 min), pH (1.2 to 10), adsorbent dose

(0.001g to 0.08g) and concentration of different salts i.e., NaCl, KCl as well as CaCl₂ (0g/L to 0.2g/L). Temperature for all experiments was maintained at 20°C with shaking speed of 120 rpm, Cd (II) ions concentration of 200 mg/L and neutral pH (except pH study). The nano hydrogel dose used for each study was 0.05g and time of adsorption was 90 min unless otherwise specified. Once the adsorption equilibrium was achieved, % removal of adsorbate and adsorption capacity of adsorbent can be calculated using Eq. 1:

$$q_e = \frac{C_0 - C_e}{M} \times V \tag{1}$$

where C_0 and C_e refers to concentrations of Cd (II) ions in solution (mg/l) both before and after adsorption, V denote used volume (mL) of solution and M adsorbent weight (g) correspondingly. For investigating effect of solution pH on swelling property of prepared nano hydrogel, 0.05g of it was immersed in solutions of varying pH i.e., 3 to 10. After immersion period, filtration of nano hydrogel was carried out for removing excess water and its weight was measured again. Afterwards, swelling ratios calculation was done by Eq. 2:

$$\text{Swelling ratio (\%)} = \frac{W_s - W_d}{W_d} \times 100 \tag{2}$$

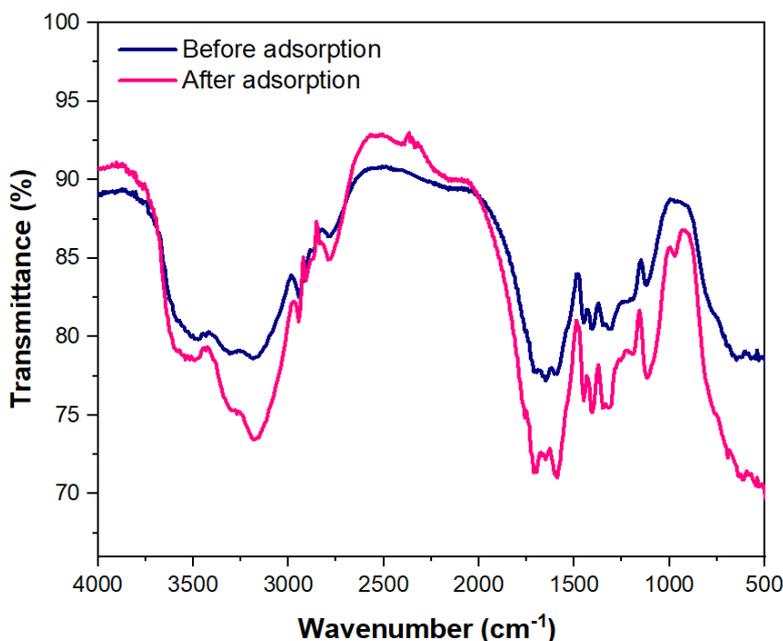


Fig. 2. FTIR results of prepared CS-g-P(CMC-co-AM) nano hydrogel both before and after Cd (II) ions adsorption.

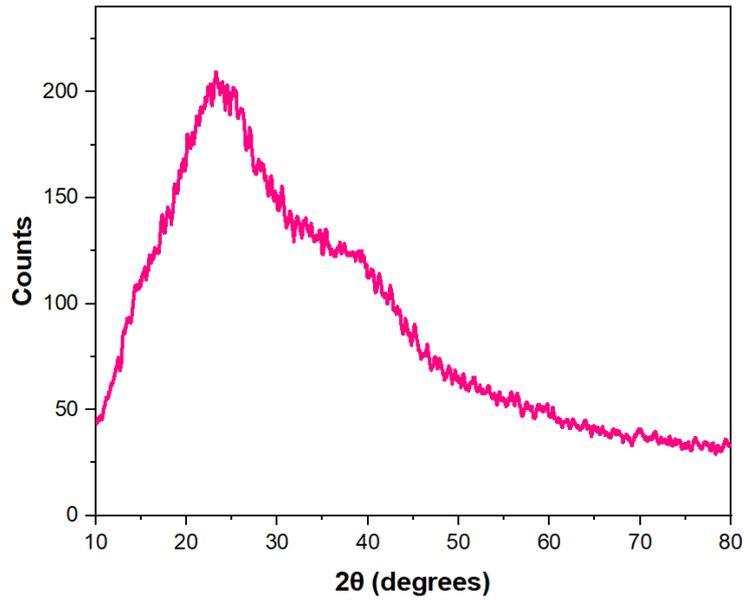


Fig. 3. XRD of prepared CS-g-P(CMC-co-AM) nano hydrogel.

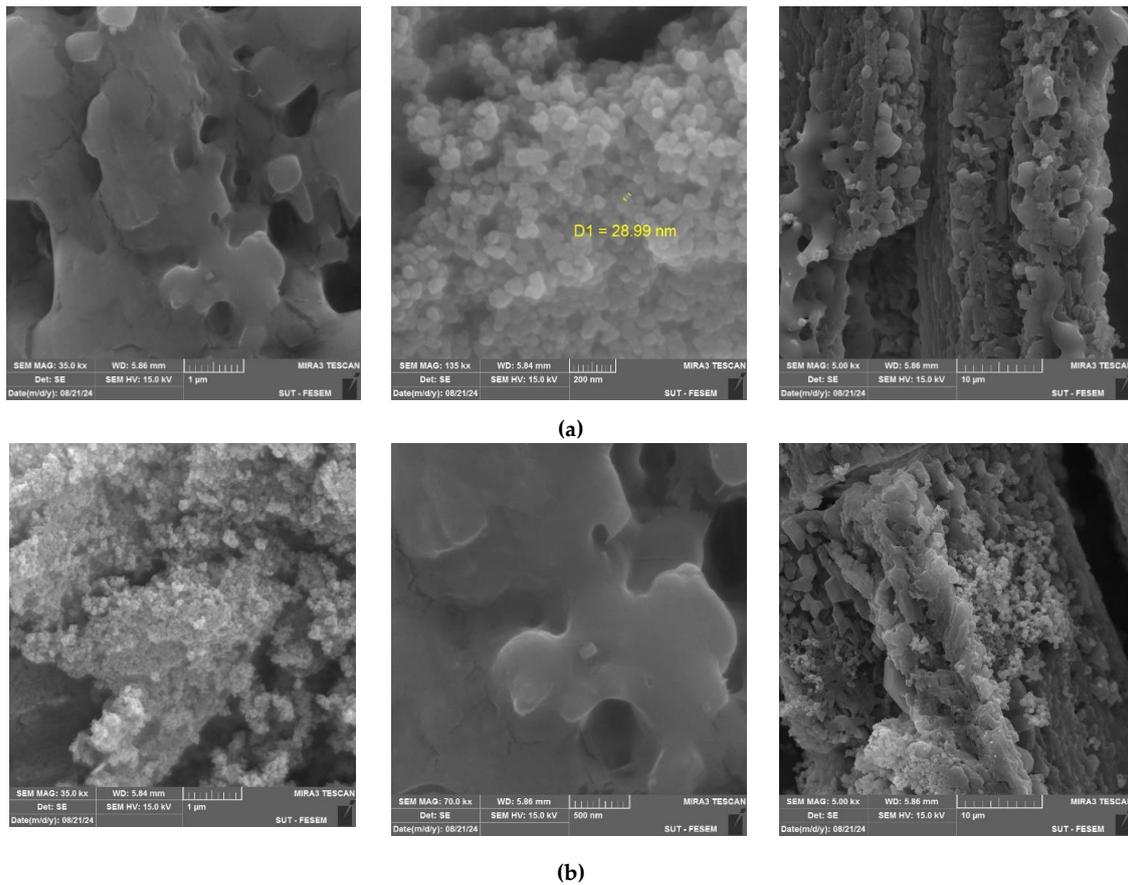


Fig. 4. FESEM of prepared CS-g-P(CMC-co-AM) nano hydrogel (a) before and (b) after adsorption.

here, and refers to weight of nano hydrogel that gets swelled and weight before swelling (dried form) correspondingly.

Two different kinetic models namely pseudo first as well as pseudo second model applied to data obtained from kinetic study. Pseudo first order model assumes that adsorption rate has direct relation with number of available adsorption sites of adsorbent. In contrast, pseudo second model assumes that adsorption rate is directly related with square of available adsorption sites.

Expressions for pseudo first and pseudo second order model are given in Eqs.3 and 4 respectively:

$$\log(Q_e - Q_t) = \log Q_e - \frac{k_1}{2.303} t \tag{3}$$

$$\frac{t}{Q_t} = \frac{1}{k_2 Q_e^2} + \frac{t}{Q_e} \tag{4}$$

here (mg/g) and (mg/g) refers to adsorbate amount adsorbed at time (min) and at equilibrium,

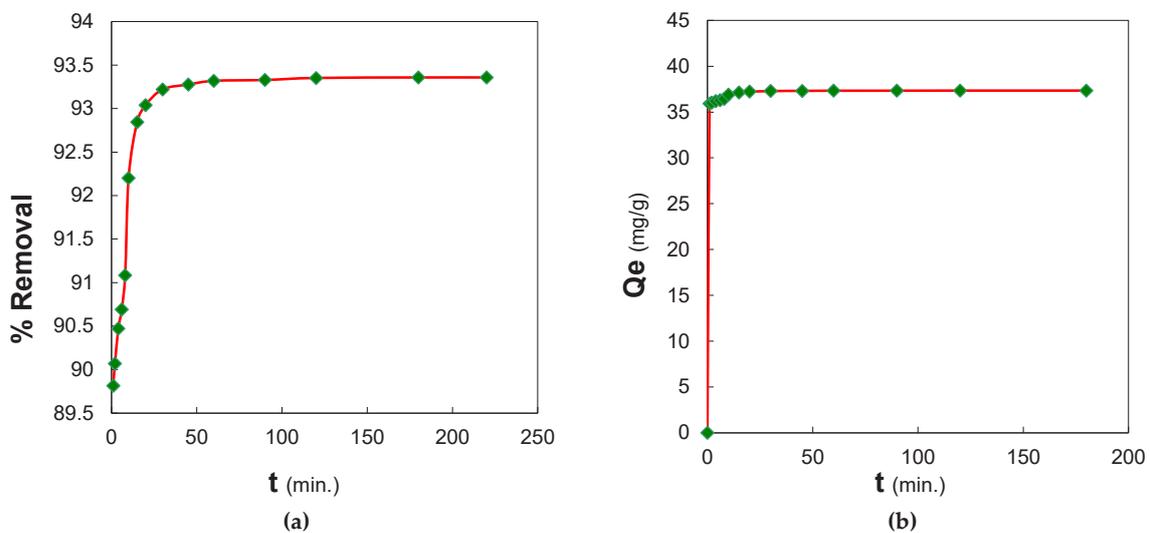


Fig. 5. Effect of time on adsorption of Cd (II) ions on prepared nano hydrogels in terms of (a) percentage removal and (b) (mg/ g).

Table 1. Effect of time on adsorption of Cd (II) ions on prepared nano hydrogels in terms of percentage removal as well as (mg/ g).

Time (min)	% Removal	q _e (mg/ g)
0	0	0
1	89.81462585	35.92585034
2	90.069161	36.0276644
4	90.47335601	36.1893424
6	90.69070295	36.27628118
8	91.08446712	36.43378685
10	92.20124717	36.88049887
15	92.8446712	37.13786848
20	93.04081633	37.21632653
30	93.22165533	37.28866213
45	93.27664399	37.3106576
60	93.3185941	37.32743764
90	93.32879819	37.33151927
120	93.35204082	37.34081633
180	93.35770975	37.3430839
220	93.35770975	37.3430839

correspondingly. Further, (1/min) and (g/mgmin) are rate constant for pseudo-first and second model correspondingly [37].

RESULTS AND DISCUSSION

Characterization study

The FTIR spectra of CS-g-P(CMC-co-AM) nano hydrogel before and after Cd (II) ion adsorption revealed significant changes, providing insights into adsorption mechanism. Before adsorption (Fig. 2), the broad peak at 3400-3200 cm⁻¹ indicated the presence of hydroxyl and amide groups. After adsorption, a shift in these peak suggested interactions with Cd (II) ions. Furthermore, the peak at 2900 cm⁻¹, associated with C-H stretching, remained relatively unchanged. However, significant changes were observed in 1750-1500 cm⁻¹ region [5, 17, 19, 38, 39]. Results revealed that peaks related to C=O stretching of carboxylate groups undergo shifting in both

intensity and position highlighting the presence of strong interactions between adsorbent functional groups and Cd (II) ions. Peaks around 1000-1200 cm⁻¹, attributed to C-O stretching, also undergo changes, that further corroborate the contribution of hydroxyl as well as carboxylate groups in Cd (II) ions removal. This variation in peaks highlight the contribution of hydroxyl, carboxylate, and amide functional groups of prepared nano hydrogels for cadmium ions adsorption [38, 40-46].

The crystallographic study of nano hydrogel (Fig. 3) revealed the presence of broad peak present nearly at 2θ of 20°. The peak corresponds to an amorphous structure of nano hydrogel due to the lack of long-range crystallinity. The highly amorphous nature of the nano hydrogel is mainly responsible for Cd (II) ions adsorption [47].

The morphological analysis of nano hydrogel is shown in Fig. 4 highlighting the presence of numerous pores and heterogeneity in its structure. This porous structure is responsible

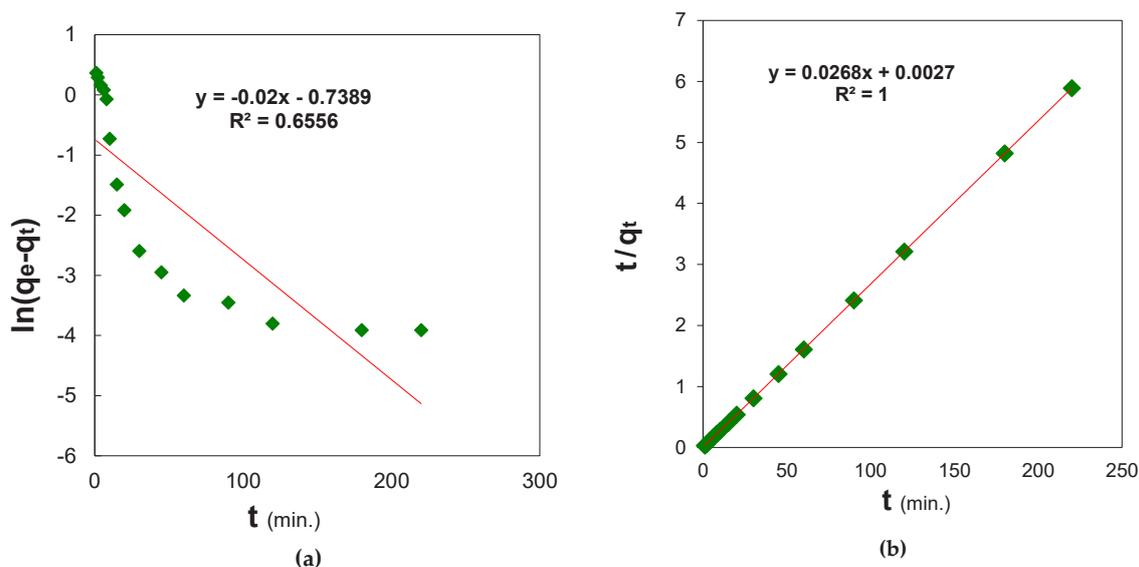


Fig. 6. Plot of (a) pseudo first and (b) pseudo second model for adsorption of Cd (II) ions onto prepared nano hydrogels.

Table 2. Parameters calculated from pseudo first and pseudo second models. Experimental (mg/g) = 37.34 mg/g.

Model	Pseudo-first order	Pseudo-second order
q _e (mg/g)	0.477	37.31
R ² values	0.6556	1
Constant	0.02	0.266
	K ₁ (1/min)	K ₂ (g/mg · min)



for providing numerous adsorption sites for Cd (II) ions adsorption thereby results in improving its adsorption capacity. Study revealed that after adsorption of Cd (II) ions, the structure of nano hydrogel transit from heterogeneous to homogeneous one signifying saturation of active sites present on adsorbent surface with adsorbed Cd (II) ions [10, 48].

Kinetic modeling

The results of contact time study in terms of % removal as well as adsorption capacity are shown

in Fig. 5 and Table 1 highlighting the direct relation of adsorption time with Cd (II) ions removal. With increasing time from 1 min to 220 min, there was an increment in both percentage removal (from 89.81% to 93.357%) and adsorption capacity (increased from 35.92 mg/g to 37.343 mg/g). This can be better explained by accessibility of free active sites on adsorbent that allows maximum number of ions to get adsorb on adsorbent surface. However, no significant change was observed in Cd (II) ions adsorption after 90 min and 220 min where removal percentage was 93.32% and

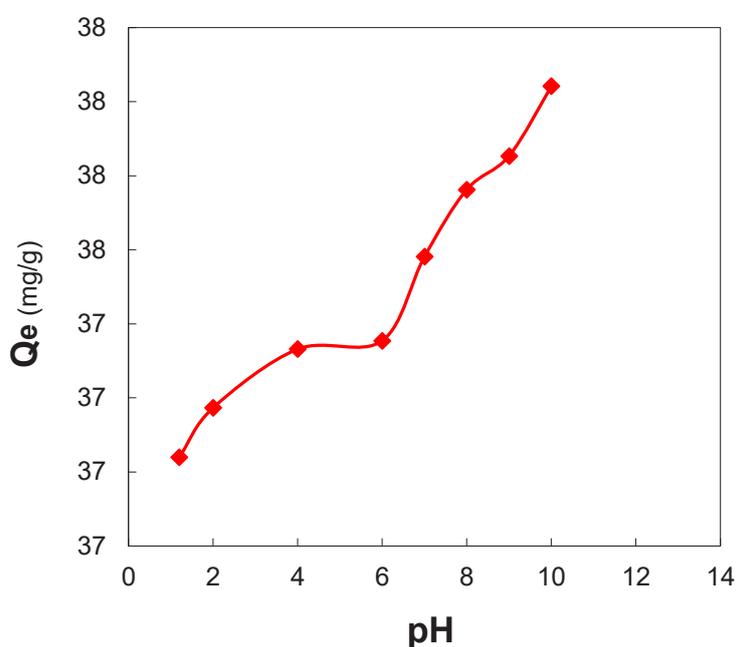


Fig. 7. Effect on pH on adsorption of Cd (II) ions on prepared nano hydrogel.

Table 3. Effect on pH on adsorption of Cd (II) ions on prepared nano hydrogel.

pH	q _e (mg/ g)
1.2	37.03922902
2	37.17301587
4	37.33174603
6	37.35442177
7	37.58117914
8	37.76258503
9	37.85328798
10	38.0414966

93.35% and adsorption capacity observed to be 37.33 mg/g and 37.343 mg/g respectively. Due to this slight variation in results, 90 minutes was selected as the optimal contact time [5].

The results of kinetic study for pseudo first order and pseudo second order model are shown in Fig. 6a and 6b respectively. It was observed that there exists greater difference between calculated (0.02 mg/g) as well as experimental [37.34 mg/g]

adsorption capacities for pseudo first model. Additionally, value of regression coefficient also observed to be lesser i.e., 0.6556 when compared with the results of pseudo second order model. These finding revealed the unsuitability of pseudo first model with the studied data. Owing to $R^2 = 1$ and less variation between experimental q_e (37.34 mg/g) and calculated q_e (37.31 mg/g), as summarized in Table 2, pseudo second order

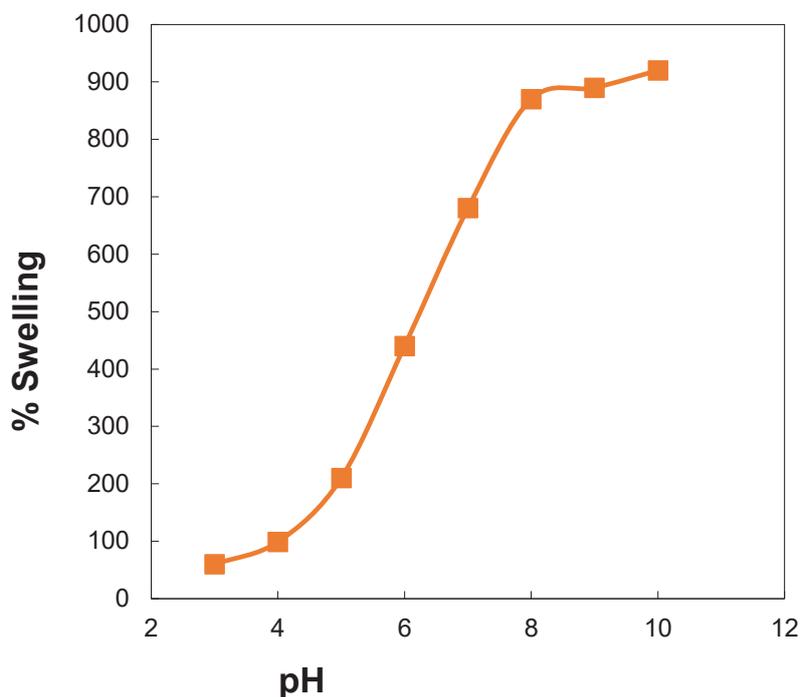


Fig. 8. Effect of pH on swelling ratio of prepared nano hydrogel.

Table 4. Effect of pH on swelling ratio of nano hydrogel.

pH	Swelling %
3	60.0
4	99.0
5	210.0
6	440.0
7	680.0
8	870.0
9	890.0
10	920.0

model fits best to studied adsorption process. The fitness of pseudo second model confirmed the chemical adsorption between adsorbent surface and Cd (II) ions [49].

Effect of solution pH

Solution pH is an important parameter that affect the charge of both adsorbent surface and adsorbate thereby affecting the overall adsorption capacity of adsorbent. To optimize best pH for study, experiments were carried out by varying pH (Fig. 7 and Table 3). Results showed that by increasing pH from acidic to basic, there was an increment in adsorption capacity of nano hydrogel. Adsorption capacity of 37.03 mg/g and 38.04 mg/g was observed by increasing pH from 1.2 to 10 respectively. Reason behind this was that at lower solution pH, i.e., acidic pH, the surface of

adsorbent become positively charged that result in causing repulsions between positive Cd (II) ions and positively charged adsorbent surface. However, increasing pH from acidic to basic results in inducing native charge on adsorbent surface that thereby results in adsorbing cationic Cd (II) ions via electrostatic attraction [9].

Swelling property of prepared nano hydrogel was investigated by varying solution pH from 3 to 10 (Fig. 8 and Table 4). It was observed that at lower solution pH i.e., 3, minimal swelling i.e., 60% can be observed. This swelling was increased to 920% when solution pH was 10. The reason behind this behaviour is that at lower pH values, water absorption was less due to the compact structure of nano hydrogel. However, an increase in solution pH allow for greater water uptake thus results in remarkable increase in swelling ratio [35].

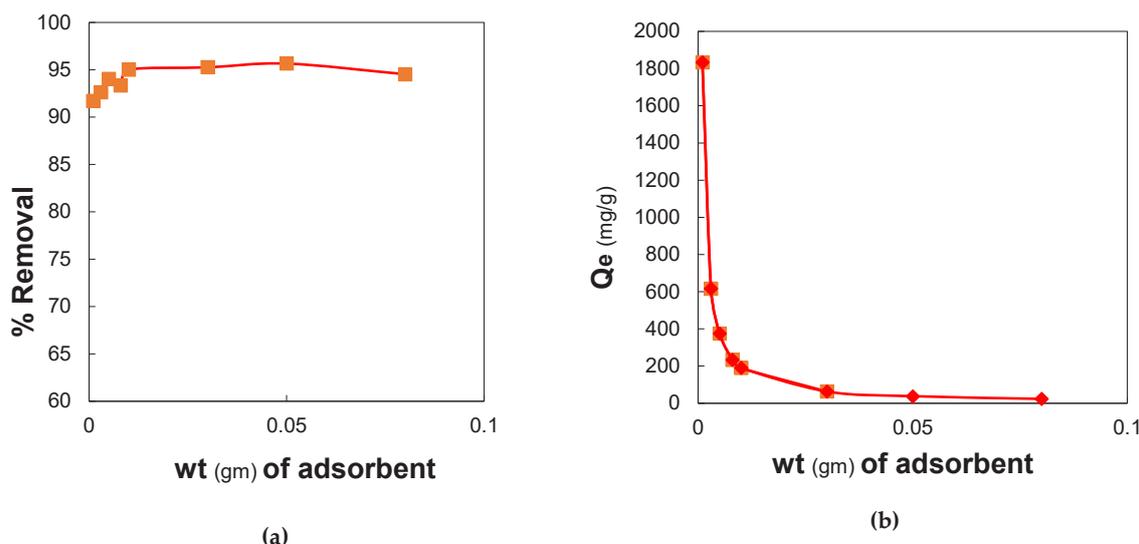


Fig. 9. Influence of nano hydrogel dosage on adsorption of Cd (II) ions in terms of (a) % removal and (b) (mg/ g)

Table 5. Influence of nano hydrogel dosage on adsorption of Cd (II) ions in terms of % removal and (mg/ g).

Adsorbent dose (g)	% Removal	Q _e (mg/g)
0.001	91.70805	1834.161
0.003	92.62642	617.5094
0.005	94.01345	376.0538
0.008	93.35771	233.3943
0.01	95.00737	190.0147
0.03	95.2585	63.50567
0.05	95.65533	38.26213
0.08	94.53458	23.63365

Effect of nano hydrogel dose and salt concentration

Effect of adsorbent dose on adsorption of Cd (II) both in terms of % removal and adsorption capacity were studied and results are presented in Fig. 9 and Table 5. It was observed that increasing nano hydrogel dose from 0.001g to 0.05g, there was an increment in % removal i.e., from 91.70% to 95.65% respectively. This was mainly due to the increased availability of active sites for adsorption of Cd (II) ions with an increase in adsorbent dose. However, with further increase in adsorbent dose to 0.08g, a decrease in % removal i.e., 94.53% was observed that might be due to agglomeration effect of adsorbent particles at higher dose. In terms of adsorption capacity, an inverse relation

with an increase in adsorbent dose was observed i.e., by increasing dose from 0.001g to 0.08g, there was a continuous decrease in adsorption capacity from 1834.14 mg/g to 23.63 mg/g respectively. The reason of this trend was that with an increased % removal of Cd (II) ions, the availability of free active sites for more adsorption decreased (since maximum adsorption sites are occupied by the adsorbate) thereby results in decreasing adsorption capacity [12, 35].

Adsorption capacity of prepared nano hydrogels was also investigated in presence of different salts i.e., NaCl, KCl and CaCl₂. Findings of study (Fig. 10 and Table 6) revealed that the adsorption capacity of adsorbent increased with an increase in

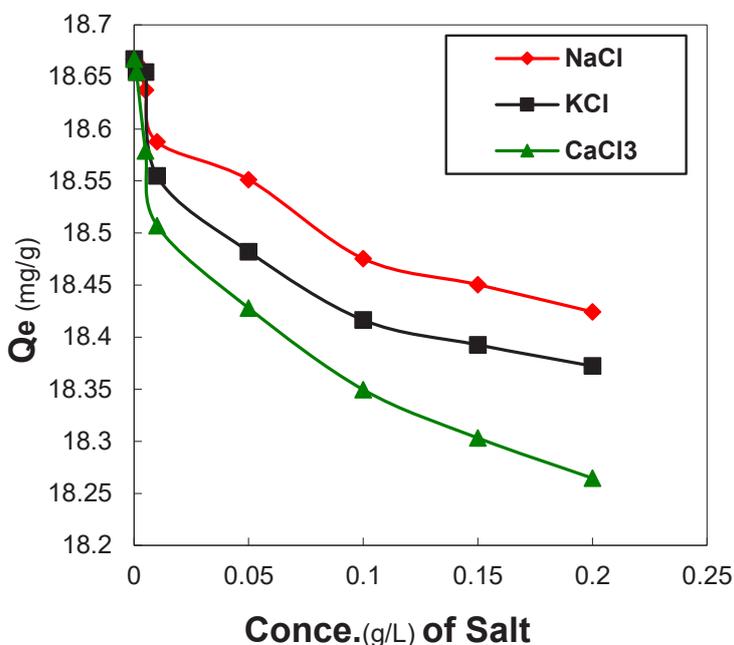


Fig. 10. Effect of different salts on adsorption of Cd (II) ions on prepared nano hydrogel.

Table 6. Effect of different salts on adsorption of Cd (II) ions on prepared nano hydrogel.

Cd (II) ions C ₀	Salt concentration (g/L)	Q _e (mg/g)		
		NaCl	KCl	CaCl ₂
200	0	18.66701	18.66701	18.66701
200	0.001	18.66361	18.65454	18.65465
200	0.005	18.63753	18.65454	18.57868
200	0.01	18.58764	18.55476	18.50726
200	0.05	18.55136	18.4822	18.42789
200	0.1	18.4754	18.41644	18.34956
200	0.15	18.45045	18.39263	18.30317
200	0.2	18.42438	18.37222	18.26451

concentration of all salts being studied. However, the maximum results were obtained with NaCl when compared with KCl and CaCl_2 due to the competitive effect of Cd (II) ions with ions of KCl and CaCl_2 .

CONCLUSION

Results of the study highlight the adsorptive potential of prepared poly (carboxymethyl cellulose-co-acrylamide) (CS-g-P(CMC-co-AM)) nano hydrogel to adsorb Cd (II) ions from water. Characterization of prepared nano hydrogels revealed presence of ionic functional groups within the nano hydrogel, chiefly hydroxyl, carboxylate, and amide groups that are mainly responsible for adsorption of Cd (II) ions on its heterogeneous and amorphous surface. Results of batch adsorption studies showed that adsorption efficiency increased with an increase in contact time and equilibrium was achieved within 90 minutes at higher pH levels (i.e., 10). The process followed pseudo-second kinetic model, suggestive of chemically controlled mechanism. The study highlights that the CS-g-P(CMC-co-AM) nano hydrogel is a low-cost, efficient adsorbent for removing cadmium ions from water.

CONFLICT OF INTEREST

The authors declare that there is no conflict of interests regarding the publication of this manuscript.

REFERENCES

- Wang FY, Wang H, Ma JW. Adsorption of cadmium (II) ions from aqueous solution by a new low-cost adsorbent—Bamboo charcoal. *J Hazard Mater.* 2010;177(1-3):300-306.
- Batool M, Javed T, Wasim M, Zafar S, Din MI. Exploring the usability of *Cedrus deodara* sawdust for decontamination of wastewater containing crystal violet dye. *Desalination and Water Treatment.* 2021;224:433-448.
- Radia ND, Essa SM, Aljeboree AM, Abed Jawad M. Evaluation of the Adsorption Efficiency of Biopolymer Hydrogel Nanocomposite/Nanoclay in Wastewater Dye Removal. *Asian Journal of Water, Environment and Pollution.* 2024;21(4):47-54.
- Ghzal Q, Javed T, Batool M. Potential of easily prepared low-cost rice husk biochar and burnt clay composite for the removal of methylene blue dye from contaminated water. *Environmental Science: Water Research and Technology.* 2023;9(11):2925-2941.
- Majeed HJ, Idrees TJ, Mahdi MA, Abed MJ, Batool M, Yousefi SR, et al. Synthesis and application of novel sodium carboxy methyl cellulose-g-poly acrylic acid carbon dots hydrogel nanocomposite (NaCMC-g-PAAC/ CDs) for adsorptive removal of malachite green dye. *Desalination and Water Treatment.* 2024;320:100822.
- Mannan HA, Nadeem R, Bibi S, Javed T, Javed I, Nazir A, et al. Mesoporous activated TiO_2 based biochar synthesized from fish scales as a proficient adsorbent for deracination of heavy metals from industrial efflux. *J Dispersion Sci Technol.* 2022;45(2):329-341.
- Shah A, Manning G, Zakharova J, Arjunan A, Batool M, Hawkins AJ. Particle size effect of *Moringa oleifera* Lam. seeds on the turbidity removal and antibacterial activity for drinking water treatment. *Environmental Chemistry and Ecotoxicology.* 2024;6:370-379.
- Shah A, Arjunan A, Thumma A, Zakharova J, Bolarinwa T, Devi S, et al. Adsorptive removal of arsenic from drinking water using KOH-modified sewage sludge-derived biochar. *Cleaner Water.* 2024;2:100022.
- Shah A, Zakharova J, Batool M, Coley MP, Arjunan A, Hawkins AJ, et al. Removal of cadmium and zinc from water using sewage sludge-derived biochar. *Sustainable Chemistry for the Environment.* 2024;6:100118.
- Arshad R, Javed T, Thumma A. Exploring the efficiency of sodium alginate beads and *Cedrus deodara* sawdust for adsorptive removal of crystal violet dye. *J Dispersion Sci Technol.* 2023;45(12):2330-2343.
- Javed T, Thumma A, Uddin AN, Akhter R, Babar Taj M, Zafar S, et al. Batch adsorption study of Congo Red dye using unmodified *Azadirachta indica* leaves: isotherms and kinetics. *Water Practice and Technology.* 2024;19(2):546-566.
- Rehman H, Javed T, Thumma A, Uddin AN, Singh N, Baig MM, et al. Potential of easily available low-cost raw cotton for the elimination of methylene blue dye from polluted water. *Desalination and Water Treatment.* 2024;318:100319.
- Bukhari A, Javed T, Haider MN. Adsorptive exclusion of crystal violet dye from wastewater by using fish scales as an adsorbent. *J Dispersion Sci Technol.* 2022;44(11):2081-2092.
- Imran MS, Javed T, Areej I, Haider MN. Sequestration of crystal violet dye from wastewater using low-cost coconut husk as a potential adsorbent. *Water Sci Technol.* 2022;85(8):2295-2317.
- Urooj H, Javed T, Taj MB, Nouman Haider M. Adsorption of crystal violet dye from wastewater on *Phyllanthus emblica* fruit (PEF) powder: kinetic and thermodynamic. *Int J Environ Anal Chem.* 2023;104(19):7474-7499.
- Alzayd AAM, Radia ND. Novel pH-sensitive of organic composite (kc-g-poly(AAc-co-AAm)/bentonite), synthesis and characterization candidate as a carrier for controlled release system in vitro to some drugs. *Carbon Letters.* 2024;34(1):505-517.
- Bayati-Komitaki N, Ganduh SH, Alzaidy AH, Salavati-Niasari M. A comprehensive review of Co_3O_4 nanostructures in cancer: Synthesis, characterization, reactive oxygen species mechanisms, and therapeutic applications. *Biomedicine and Pharmacotherapy.* 2024;180:117457.
- Hosseini M, Ghanbari M, Alzaidy AH, Dawi EA, Mahdi MA, Jasim LS, et al. Synthesis and characterization of $\text{Fe}_2\text{SiO}_4/\text{Fe}_2\text{O}_3/\text{g-C}_3\text{N}_4$ ternary heterojunction photocatalyst with enhanced photocatalytic activity under visible light. *Int J Hydrogen Energy.* 2024;60:1370-1382.
- Razavi FS, Mahdi MA, Ghanbari D, Dawi EA, Abed MJ, Ganduh SH, et al. Fabrication and design of four-component $\text{Bi}_2\text{S}_3/\text{CuFe}_2\text{O}_4/\text{CuO}/\text{Cu}_2\text{O}$ nanocomposite as new active materials for high performance electrochemical hydrogen storage application. *Journal of Energy Storage.* 2024;94:112493.
- Shah A, Arjunan A, Manning G, Batool M, Zakharova J, Hawkins AJ, et al. Sequential novel use of *Moringa*

- oleifera Lam., biochar, and sand to remove turbidity, E. coli, and heavy metals from drinking water. *Cleaner Water*. 2024;2:100050.
21. Pérez-Marín AB, Zapata VM, Ortuño JF, Aguilar M, Sáez J, Lloréns M. Removal of cadmium from aqueous solutions by adsorption onto orange waste. *J Hazard Mater*. 2007;139(1):122-131.
 22. Pyrzynska K. Removal of cadmium from wastewaters with low-cost adsorbents. *Journal of Environmental Chemical Engineering*. 2019;7(1):102795.
 23. Sen TK, Mohammad M, Maitra S, Dutta BK. Removal of Cadmium from Aqueous Solution Using Castor Seed Hull: A Kinetic and Equilibrium Study. *CLEAN – Soil, Air, Water*. 2010;38(9):850-858.
 24. Shin EW, Karthikeyan KG, Tshabalala MA. Adsorption mechanism of cadmium on juniper bark and wood. *Bioresour Technol*. 2007;98(3):588-594.
 25. Tran HN, You S-J, Chao H-P. Thermodynamic parameters of cadmium adsorption onto orange peel calculated from various methods: A comparison study. *Journal of Environmental Chemical Engineering*. 2016;4(3):2671-2682.
 26. Vázquez G, González-Álvarez J, Freire S, López-Lorenzo M, Antorrena G. Removal of cadmium and mercury ions from aqueous solution by sorption on treated Pinus pinaster bark: kinetics and isotherms. *Bioresour Technol*. 2002;82(3):247-251.
 27. Zheng W, Li X-m, Wang F, Yang Q, Deng P, Zeng G-m. Adsorption removal of cadmium and copper from aqueous solution by areca—A food waste. *J Hazard Mater*. 2008;157(2-3):490-495.
 28. Pang Y, Zhao C, Li Y, Li Q, Bayongzhong X, Peng D, et al. Cadmium adsorption performance and mechanism from aqueous solution using red mud modified with amorphous MnO(2). *Sci Rep*. 2022;12(1):4424-4424.
 29. Lei T, Li S-J, Jiang F, Ren Z-X, Wang L-L, Yang X-J, et al. Adsorption of Cadmium Ions from an Aqueous Solution on a Highly Stable Dopamine-Modified Magnetic Nano-Adsorbent. *Nanoscale research letters*. 2019;14(1):352-352.
 30. Lapham DP, Lapham JL. BET surface area measurement of commercial magnesium stearate by krypton adsorption in preference to nitrogen adsorption. *Int J Pharm*. 2019;568:118522.
 31. Thommes M, Kaneko K, Neimark AV, Olivier JP, Rodriguez-Reinoso F, Rouquerol J, et al. Physisorption of gases, with special reference to the evaluation of surface area and pore size distribution (IUPAC Technical Report). *Pure and Applied Chemistry*. 2015;87(9-10):1051-1069.
 32. Shah A, Arjunan A, Manning G, Zakharova J, Andraulaki I, Batool M. The effect of dose, settling time, shelf life, storage temperature and extractant on Moringa oleifera Lam. protein coagulation efficiency. *Environmental Nanotechnology, Monitoring and Management*. 2024;21:100919.
 33. Jiang Z, Han X, Zhao C, Wang S, Tang X. Recent Advance in Biological Responsive Nanomaterials for Biosensing and Molecular Imaging Application. *Int J Mol Sci*. 2022;23(3):1923.
 34. Abdullah AR, Jasim LS. High-efficiency removal of diclofenac sodium (DS) drug using chitosan-grafted-poly(acrylic acid-co-N-isopropylacrylamide)/kaolin clay hydrogel composite. *Int J Environ Anal Chem*. 2024:1-21.
 35. Rafak SH, Jasim LS. Synthesis of novel bentonite/pectin-grafted-poly(crotonic acid-co-acrylic acid) hydrogel nanocomposite for adsorptive removal of safranin O dye from aqueous solution. *Int J Environ Anal Chem*. 2024:1-24.
 36. Batool M, Haider MN, Javed T. Applications of Spectroscopic Techniques for Characterization of Polymer Nanocomposite: A Review. *Journal of Inorganic and Organometallic Polymers and Materials*. 2022;32(12):4478-4503.
 37. Saruchi, Kumar V, Ghfar AA, Pandey S. Microwave Synthesize Karaya Gum-Cu, Ni Nanoparticles Based Bionanocomposite as an Adsorbent for Malachite Green Dye: Kinetics and Thermodynamics. *Frontiers in Materials*. 2022;9.
 38. Kareem NS, Mohammed SA, Abed MJ, Aneed AH, Kamal HM, Zahid NI, et al. New macrocycles incorporating glycolipids via copper-catalyzed triazole coupling. *J Carbohydr Chem*. 2022;41(1):1-17.
 39. Yasir AF, Jamel HO. Synthesis of a New DPTYEAP Ligand and Its Complexes with Their Assessments on Physical Properties, Antioxidant, and Biological Potential to Treat Breast Cancer. *Indonesian Journal of Chemistry*. 2023;23(3):796.
 40. Pathania D, Sood S, Saini AK, Kumari S, Agarwal S, Gupta VK. Studies on anticancerous and photocatalytic activity of carboxymethyl cellulose-cl-poly(lactic acid-co-itaconic acid)/ZnO-Ag nanocomposite. *Arabian Journal of Chemistry*. 2020;13(9):6966-6976.
 41. The value of two onset determination of anti-H.pylori IgM antibody in patients with dyspepsia in Iraq. *International Journal of Pharmaceutical Research*. 2020;12(02).
 42. The value of iron supplementation to children with Helicobacter pylori infection in Iraq: a cross-sectional study. *International Journal of Pharmaceutical Research*. 2020;12(02).
 43. Jamdar M, Heydariyan Z, Alzaidy AH, Dawi EA, Salavati-Niasari M. Eco-friendly auto-combustion synthesis and characterization of SmMnO₃/Sm₂O₃/Mn₂O₃ nanocomposites in the presence of saccharides and their application as photocatalyst for degradation of water-soluble organic pollutants. *Arabian Journal of Chemistry*. 2023;16(12):105342.
 44. Kennen JG, Stein ED, Webb JA. Evaluating and managing environmental water regimes in a water-scarce and uncertain future. *Freshwater Biology*. 2018;63(8):733-737.
 45. Mahdi MA, Oroumi G, Samimi F, Dawi EA, Abed MJ, Alzaidy AH, et al. Tailoring the innovative Lu₂CrMnO₆ double perovskite nanostructure as an efficient electrode materials for electrochemical hydrogen storage application. *Journal of Energy Storage*. 2024;88:111660.
 46. Rahimkhoei V, Alzaidy AH, Abed MJ, Rashki S, Salavati-Niasari M. Advances in inorganic nanoparticles-based drug delivery in targeted breast cancer theranostics. *Advances in Colloid and Interface Science*. 2024;329:103204.
 47. Awad MA, Jasim Al-Hayder LS. Removal of a Bsoprolol drug from Aqueous Solutions onto Graphene Oxide/ Carboxymethyl cellulose sodium / Acryl acid polymer Composite by Adsorption. *IOP Conference Series: Materials Science and Engineering*. 2020;928(5):052033.
 48. Sun Z, Yin Y, An Y, Deng C, Wei Z, Jiang Z, et al. A novel modified carboxymethyl cellulose hydrogel adsorbent for efficient removal of poisonous metals from wastewater: Performance and mechanism. *Journal of Environmental Chemical Engineering*. 2022;10(4):108179.
 49. Abbas SS, Jasim LS. Removal of rhodamine B from aqueous solution by montmorillonite/poly (malic acid-co-acrylic acid): Thermodynamic study. *AIP Conference Proceedings: AIP Publishing*; 2023. p. 020013.