

RESEARCH PAPER

Preparation and Superabsorbent of a Novel Copolymer Nanocomposite: Optimization of Swelling Behavior

Nadher D. Radia¹, Aseel M. Aljeboree², Ayad F. Alkaim^{2*}, Mohammed Abed Jawad³

¹ Department of Chemistry, College of Education, University of Al-Qadisiyah, Al-Qadisiyah, Iraq

² Department of Chemistry, College of Sciences for Girls, University of Babylon, Hilla, Iraq

³ Department of Pharmaceuticals, Al-Nisour University College, Baghdad, Iraq

ARTICLE INFO

Article History:

Received 12 May 2025

Accepted 24 August 2025

Published 01 October 2025

Keywords:

Acrylamide

Carboxymethyl cellulose

Hydrogel

Itaconic acid

Nanocomposite

ABSTRACT

Biosorbents are environmentally friendly, readily available, have high absorption efficiency, and are desirable for the treatment of contaminated water. Herein, a covalently cross-linked green macro particle hydrogel nanocomposite CMC(IA-coAm-Ca) as a bio-adsorbent was prepared through a polysaccharide carboxymethyl cellulose reaction with acrylamide (Am)-Itaconic acid (IA) modified carboxymethyl cellulose (CMC) and further Ca(II) crosslinking polymerization. To limit the structure and characteristics of the nanocomposite composite several techniques were used such as (HRTEM), (FESFM/EDX), (XRD), and (FTIR). The practical experiments included the study of improving the preparation conditions produced by a nanocomposite with the maximum SR%: the effect concentration of CMC, the effect of Am, the effect of IA, the effect of Ca(II) ion crosslinking effect of pH, and effect of temperature. The results show that employing (1 g) CMC, (2 g) Am, 2 ml IA, and (2 g) Ca(II) ion crosslinking. The hydrogel nanocomposites highest swelling ratio SR% in DW was 2100%. It was found that the mechanical water retention properties are strongly affected by monomer to CMC ratio and concentration of Ca(II) ion crosslinking. thus, the hydrogel displayed swelling behaviors that were monomers-dependent.

How to cite this article

Radia N., Aljeboree A., Alkaim A., Jawad M. Preparation and Superabsorbent of a Novel Copolymer Nanocomposite: Optimization of Swelling Behavior. J Nanostruct, 2025; 15(4):1733-1740. DOI: 10.22052/JNS.2025.04.022

INTRODUCTION

Hydrogels are described as having a three-dimensional network. They are classified as polymers that can swell significantly and also maintain their shape and structure in water over long periods of time. Hydrogels maintain their structure and cross-linked nature of each polymer chain, which enables them to retain a large amount of water. [1] Hydrogels are prepared

by cross-linking polymer chains chemically or physically to form a network three-dimensional. Hydrogels are characterized by their high-water absorption capacity due to their crystalline network and high swelling capacity; however, they are not able to dissolve in water. Therefore, bio-based hydrogels have gained biocompatibility, environmental friendliness, and biodegradability. It is not enough for hydrogels to consume large

* Corresponding Author Email: alkaimayad@gmail.com



amounts of water or biological fluids due to their high swelling capacity and remain insoluble in water. Biopolymer-based hydrogels have gained popularity due to their biocompatibility, swelling capacity, low-cost, high-water absorption, and biodegradability.[2]. Differences in the structure and composition of the polymer affect the crosslinking of the biopolymer and the different methods of crosslinking. For example, the great ability of biopolymers to swell and absorb water leads to Various applications such as in medicine and agriculture such as using them as wound dressings, personal care products, sanitary pads and diapers. [1, 3]. Poly-acrylamide is the primary network in several tough hydrogels. Poly acrylamide hydrogels containing salts are utilized as stretchable, transparent, ionic conductors in ionotropic. Polyacrylamide hydrogels have been utilized as a model material to study the growth of cracks in hydrogels under static cyclic and dynamic loads [4, 5]. Carboxy methyl cellulose (CMC) is a soluble in-water cellulose derivative that is bio-compatible and can be further chemically modified to form gel through physical interactions [6-8]. CMC is a soluble in water, anionic polysaccharide and is one of the most commonly used industrial cellulose ether. CMC is applied in systems where hydrophilic colloids are involved and has some applications in some industrial areas, including cosmetics, detergents, pharmaceuticals, textiles, food, etc. CMC displays the capability to suspend solids in an aqueous solution, stabilize emulsions, absorb moisture from the atmosphere, and is mostly utilized as a thickener, suspending

aid, binder, gelling agent, stabilizer, and water retention agent, etc [9-12].

MATERIALS AND METHODS

Synthesis of CMC(IA-co-Am-Ca) gel

A CMC(IA-co-Am-Ca) gel was synthesized by applying polymerization. different quantities of Am (0.1–2 g/ 10 ml. After that, several quantities of CMC (0.15–4 g/ 20 ml) to 40 °C and IA (0.15–3 g/ 10 ml) the reaction mixture was stirred at 150 rpm for 90 min at 25 °C. The CMC(IA-co-Am-Ca) gel solution was dropped into a 100 mL $\text{CaCl}_2 \cdot 2\text{H}_2\text{O}$ solution of 10–40 g/L. After the reaction was completed, the gel spheres continued to be cured in solution for 3 h, then they were removed, washed in distilled water, and dried. CMC(IA-co-Am-Ca) gel spheres were then prepared. Fig. 1 shows the image of gels.

Studies of Swelling of CMC(IA-co-Am-Ca) gel

The pre-weighted CMC(IA-co-Am-Ca) gel was placed in DW and kept at 25 °C for 120 min without any disturbance. The swollen CMC(ITA/AM-Ca) gel was blotted with filter paper to eliminate the additional DW, and after that weighed. The extreme RS% was calculated by Eq. 1:

$$\% \text{ SR} = \frac{M1 - M2}{M2} \times 100 \quad (1)$$

W₁ denotes the mass of the swelled CMC(IA-co-Am-Ca) gel, and W₂ mass of the dried CMC(ITA/AM-Ca) gel.

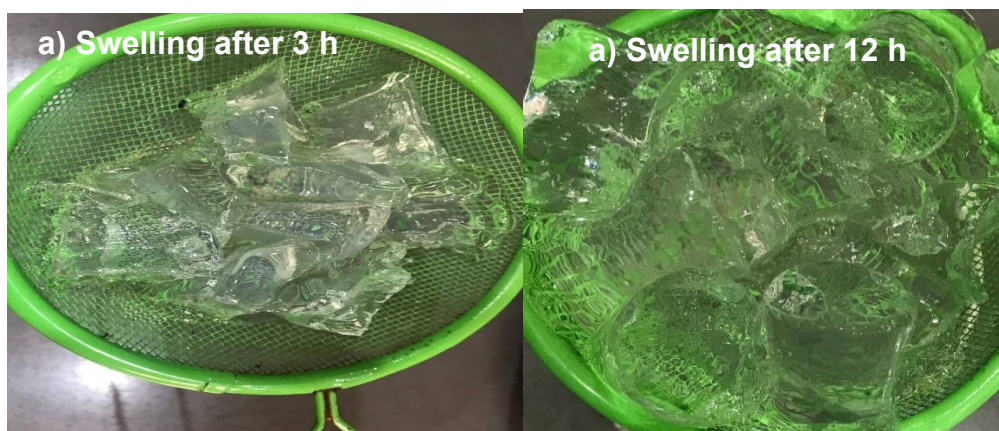


Fig. 1. Real image of preparation of CMC(IA-co-Am-Ca) gel.

RESULTS AND DISCUSSION

In the FTIR spectrum of the CMC(IA-co-Am-Ca) gel Fig. 2, The bands at $3400\text{--}3500\text{ cm}^{-1}$ arising from stretching group --OH converted to broader and fewer shifted at $3200\text{--}3400\text{ cm}^{-1}$, The broadband from 3100 to 3300 cm^{-1} indicates stretching --OH in the polysaccharide. Peaks at 980 , and 1000 cm^{-1} were assigned to C--O--C , and C--O--H stretching, of glucose stretching, respectively [13-15]. This can be interpreted as follows: A broad band from $3500\text{--}2750\text{ cm}^{-1}$ indicates --NH , --OH , and overlapping bands from asymmetric cyclic CH , --CH_2 , and --CH_3 . Moreover, shifted peaks from $1500\text{--}1330\text{ cm}^{-1}$ represent aromatic rings C=C group, indicative of interactions [16, 17].

X-ray Diffraction (XRD)

Fig. 3 shows the XRD patterns of CMC(IA-co-Am-Ca) gel nanocomposite, that appeared broad peak in CMC(ITA/AM-Ca) gel nanocomposite, non-crystalline structure in the nanocomposite diffraction pattern, A peak looked at $2\theta = 21.122^\circ$, and $2\theta = 32.141^\circ$ suggesting conversion from amorphous to semi-crystalline nature. The amorphous nature was also reported for the polymer of CMC with either IA or Am in the literature [18, 19]. This confirms the contribution of the grafting CMC. The broadness of XRD patterns for hydrogel shows the dispersal of CMC in gel [20, 21].

The FESEM morphology technique was used to determine the surface morphology of CMC(IA-co-Am-Ca) gel nanocomposite at different weights of carboxymethyl cellulose. The FESEM microscopic image revealed in the form Fig. 4a, the gel with weight 2 g of (CMC). The surface has structures resembling thin threads with random, unordered aggregates as a result of the lack of overlap of (CMC) within the gel matrix due to the lack of cohesion of the gel and its collapse at high temperatures. As for the Fig. 4b weight (3 g) the CMC of the gel has a rough surface without any crosslinking between the CMC molecules. Some small white balls in the form of small aggregates were also observed. The CMC(IA-co-Am-Ca) gel nanocomposite form also showed a porous, sheet-like surface due to gel formation and cross-linking by Ca^{+2} between the polymeric chains. At the same time, CMC(IA-co-Am-Ca) gel nanocomposite face resulting from the introduction of CMC contains rough particles within the polymeric chains. The prepared surface is characterized as a heterogeneous spongy porous surface containing voids and numerous active sites. Hence it can swelling [22, 23]. EDX analysis of the samples (Fig. 4c), that the Ca(II) ions in solution underwent a cross-linking polymerization reaction with CMC to form a CMC(IA-co-Am-Ca) gel nanocomposite with a three-dimensional network structure. The surface scan analysis of CMC(IA-co-Am-Ca) gel nanocomposite Ca, elements are

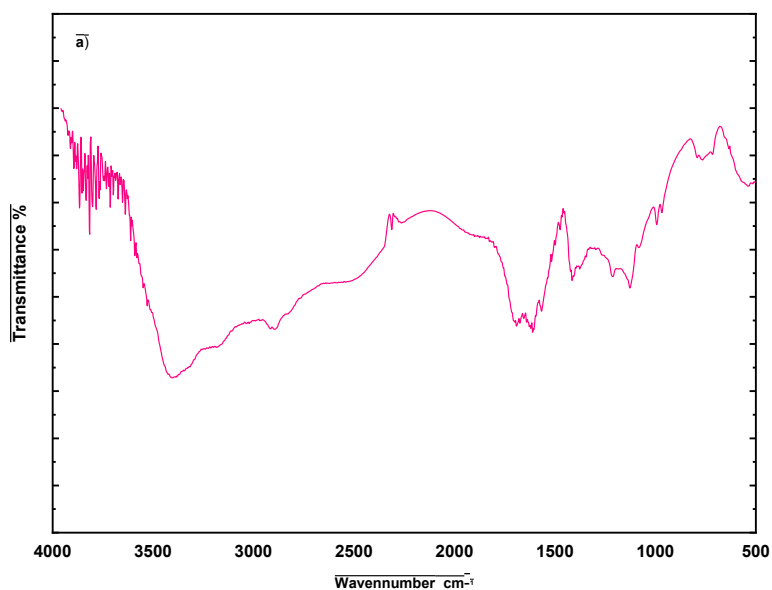


Fig. 2. FTIR spectrum of the a) CMC(IA-co-Am-Ca) gel.

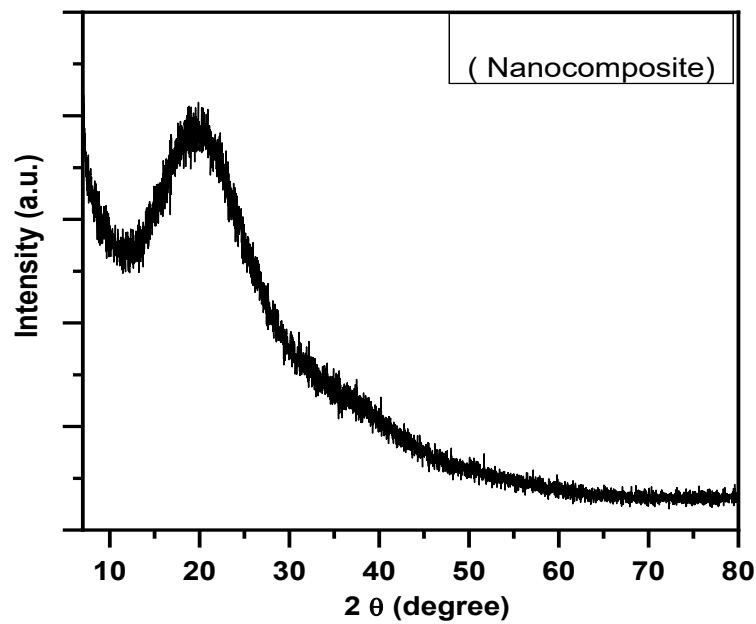


Fig. 3. XRD patterns of CMC(IA-co-Am-Ca) gel nanocomposite.

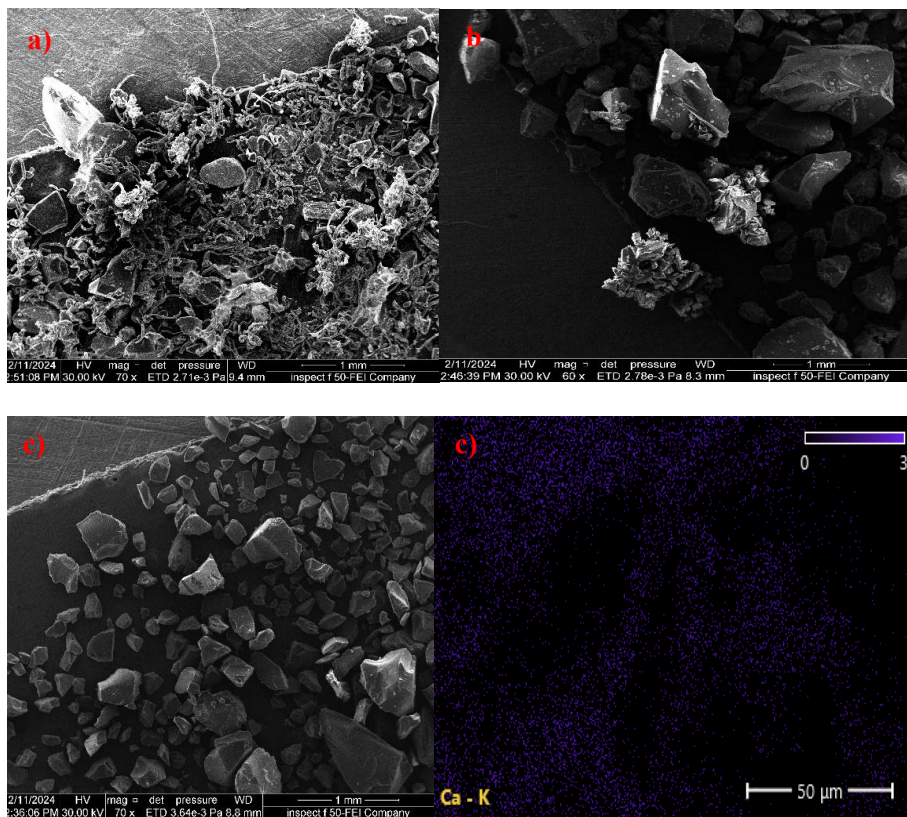


Fig. 4. FESEM a) 2 g of CMC in nanocomposite, b) 3 g CMC in nanocomposite, c) 4 g CMC in nanocomposite, d) EDX of CMC(IA-co-Am-Ca) gel nanocomposite.

evenly distributed in the composite, indicating the successful preparation of the nanocomposite [24-26].

A higher resolution transmission electron microscope (HRTEM) image is shown in Fig. 5. This figure shows a carboxymethyl cellulose CMC(IA-co-Am-Ca) gel nanocomposite embedded within a polymer matrix. It can be seen that the CMC(ITA/AM-Ca) gel nanocomposite appears in the form of small irregular random balls spread on the polymer surface with some patchy black aggregates and tends to form aggregates at 200 nm and 500 nm. Moreover, the surface of the CMC(IA-co-Am-Ca) gel nanocomposite is covered with a thin layer, in which carboxymethyl cellulose was observed incorporated within the CMC(IA-co-Am-Ca) gel and plays a pivotal part in enhancement stability

and raising the surface area as an essential component. To synthesize ecologically friendly hydrogel[27-30].

Optimization Swelling of the CMC(IA-co-Am-Ca) gel nanocomposite)

The swelling behavior of the polymer is shown in Fig. 6a as a function of the IA. Different weights of IA from (0.5-2.5 ml), which shows the effect of several concentrations of IA. The magnitude of the effect of IA on swelling is similar to the Ca(II) crosslinking ratio because the incorporation of IA also increases the mechanical strength of the polymer and reduces the swelling behavior in the water of the resulting polymer, which occurs through the ability of IA to cross-link [31].

Fig. 6b displays the swelling capability of

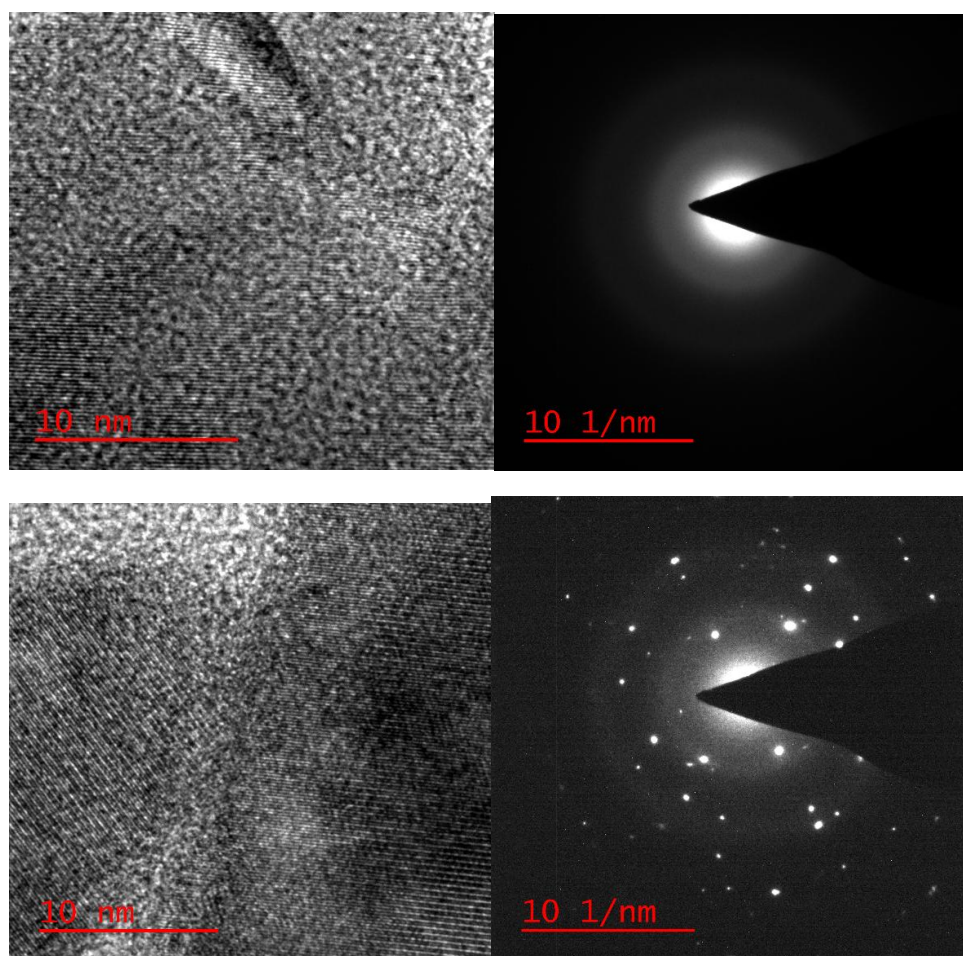


Fig. 5. Higher resolution transmission electron microscopy (HRTEM) image of CMC(IA-co-Am-Ca) gel nanocomposite)

nanocomposite with several concentrations of CMC (0.1–2g/20 ml). The RS% is firstly very low due to the repulsion between the negative charge caused via pairs of electrons on O₂ and N₂ charge on –OH in CMC. However, the rising concentration of CMC, increases cross-linking and difficulty absorbing water. As a result, the RS% rises with increasing concentration of CMC. thus, greater quantities of CMC created extra active sites, leading in cross-linking optimal to best adsorbate loading on the adsorbent [32, 33].

The effect of acrylamide (Am) concentration on the bio-composite was examined by measuring the swelling ratio. Different amounts of Am (0.1–2.5 g) were dissolved in 5 ml of DW and added

while stirring Fig. 6b, a maximum RS% of 1200% was achieved with 0.5 g. Similar to how insufficient monomer caused decreased swelling when the AM dose was less than 2.0 g, a decrease in the amount of monomer present resulted in a decrease in swelling by more than 2.0 g. Concentrations of Am above the recommended level. Absorbance may decrease with Am concentration above 1.0 g[34, 35]

To prevent the polymer chains from dissolving in water, Ca(II) was used as a cross-linker during polymer preparation. Use different amount of Ca(II) (0.1–2 g/L) via dissolving it in 100 ml of H₂O to increase the amount of cross-linker dimer. To reduce the water absorption of water absorbed

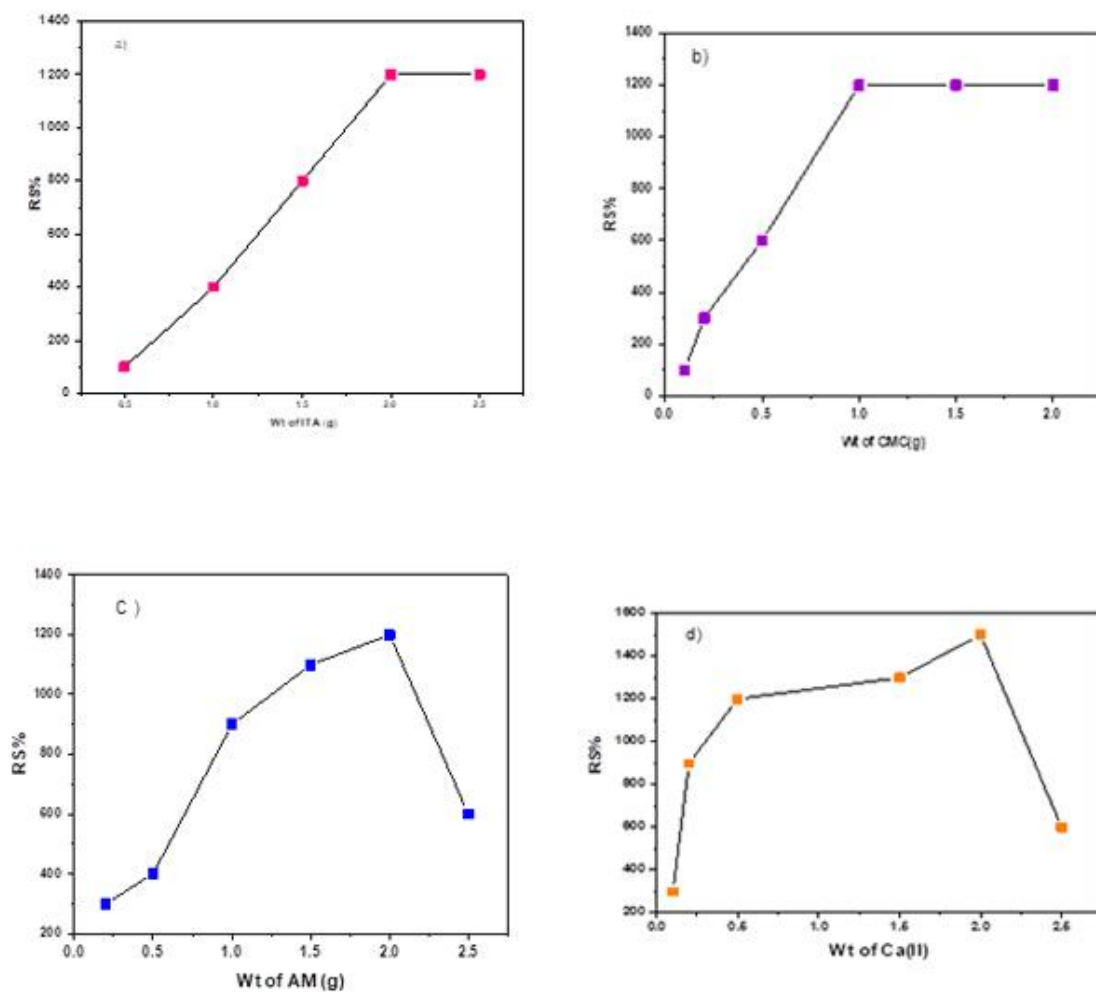


Fig. 6. Optimization Swelling of the CMC(IA-co-Am-Ca) gel nanocomposite, a) weight of IA, b) weight of CMC, c) weight of Am, and d) weight of Ca(II).

into the polymer network, which reduces the swelling ratio. Fig. 6d shows that less space among the copolymer chains resulted in more rigid 3D networks and even less surface area. The optimal mesh size for cross-linking affects the amount of contaminants trapped in the polymer due to the concentration of Ca(II) as a cross-linker. At little concentrations, the degree of crosslinking cannot adequately trap contaminant particles. Cross-linked Ca(II) was added during polymer preparation to form network crosslinks that prevent dissolution of the polymer chains in water. Increasing the concentration of calcium (II) led to a decrease in water absorption within the polymer network, which reduces the swelling behavior [33, 36].

CONCLUSION

A semi-natural, non-toxic CMC(IA-co-Am-Ca) gel nanocomposite was synthesized by polymerization of carboxymethyl cellulose (CMC). The optimization study revealed that the CMC(IA-co-Am-Ca) gel nanocomposite had a greater swelling ratio at the concentration of monomer (AM, 2 g), polysaccharide (CMC, 1g), and crosslinking Ca(II) (2 g). It has been found that the mechanical properties of water retention are strongly influenced by the monomer-to-monomer ratio and the crosslinking concentration of calcium(II) ions. The best course of swelling was presented in deionized water by approximately 1200.3 %. the RS% rises with increasing concentration of CMC. thus, greater quantities of CMC created extra active sites, leading to cross-linking optimal to best adsorbate loading on the adsorbent, Cross-linked Ca(II) was added during polymer preparation to form network crosslinks that prevent dissolution of the polymer chains in water. Increasing the concentration of calcium (II) led to a decrease in water absorption within the polymer network, which reduced the swelling behavior.

CONFLICT OF INTEREST

The authors declare that there is no conflict of interests regarding the publication of this manuscript.

REFERENCE

1. Hoque M, Alam M, Wang S, Zaman JU, Rahman MS, Johir MAH, et al. Interaction chemistry of functional groups for natural biopolymer-based hydrogel design. *Materials Science and Engineering: R: Reports*. 2023;156:100758.
2. Verma A, Sharma B, Kalia S, Alsanie WF, Thakur S, Thakur VK. Carboxymethyl cellulose based sustainable hydrogel for colon-specific delivery of gentamicin. *Int J Biol Macromol*. 2023;228:773-782.
3. Radia ND, Aljeboree AM, Mhammed AAA. Enhanced removal of crystal violet from aqueous solution using carrageenan hydrogel nanocomposite/MWCNTs. *Inorg Chem Commun*. 2024;167:112803.
4. Adsorption and Removal of pharmaceutical Riboflavin (RF) by Rice husks Activated Carbon. *International Journal of Pharmaceutical Research*. 2019;11(2).
5. Khosravi N, Youseftabar-Miri L, Divsar F, Hallajian S, Hafezi K. Development and evaluation of chitosan-g-poly(acrylic acid-co-acrylamide) hydrogel composite containing gabapentin for in vitro controlled release. *J Mol Struct*. 2022;1270:133934.
6. Morrison TX, Gramlich WM. Tunable, thiol-ene, interpenetrating network hydrogels of norbornene-modified carboxymethyl cellulose and cellulose nanofibrils. *Carbohydr Polym*. 2023;319:121173.
7. Aljeboree AM, Essa SM, Kadam ZM, Dawood FA, Falah D, Alkaim AF. Environmentally Friendly Activated Carbon Derived from Palm Leaf for the Removal of Toxic Reactive Green Dye. *International Journal of Pharmaceutical Quality Assurance*. 2023;14(01):12-15.
8. Zamani-Babgohari F, Irannejad A, Kalantari Pour M, Khayati GR. Synthesis of carboxymethyl starch co (polyacrylamide/polyacrylic acid) hydrogel for removing methylene blue dye from aqueous solution. *Int J Biol Macromol*. 2024;269:132053.
9. Yang P, Song Y, Sun J, Wei J, Li S, Guo X, et al. Carboxymethyl cellulose and metal-organic frameworks immobilized into polyacrylamide hydrogel for ultrahigh efficient and selective adsorption U(VI) from seawater. *Int J Biol Macromol*. 2024;266:130996.
10. Kunjalukkal Padmanabhan S, Lamanna L, Friuli M, Sannino A, Demitri C, Licciulli A. Carboxymethylcellulose-Based Hydrogel Obtained from Bacterial Cellulose. *Molecules*. 2023;28(2):829.
11. Hameed KAA, Radia ND. Preparation and Characterization of Graphene Oxide (Sodium Alginate-g-polyacrylic Acid) Composite: Adsorption Kinetic of Dye Rose Bengal from Aqueous Solution. *Neuroquantology*. 2022;20(3):24-31.
12. Zheng M, Cai K, Chen M, Zhu Y, Zhang L, Zheng B. pH-responsive poly(gellan gum-co-acrylamide-co-acrylic acid) hydrogel: Synthesis, and its application for organic dye removal. *Int J Biol Macromol*. 2020;153:573-582.
13. Jabeen S, Alam S, Shah LA, Ullah M. Successful preparation of tercopolymer hydrogel for the removal of toluidine dye from contaminated water: Experimental and DFT study. *Sep Sci Technol*. 2023;58(11):1923-1938.
14. Awed M, Mohamed RR, Kamal KH, Sabaa MW, Ali KA. Tosyl-carrageenan/alginate composite adsorbent for removal of Pb²⁺ ions from aqueous solutions. *BMC Chemistry*. 2024;18(1).
15. Koryam AA, El-Wakeel ST, Radwan EK, Fattah AMA, Darwish ES. Preparation and characterization of chemically cross-linked zwitterionic copolymer hydrogel for direct dye and toxic trace metal removal from aqueous medium. *Environmental Science and Pollution Research*. 2023;30(28):72916-72928.
16. Nasser A, Kareem S. Removal of methylene blue From Aqueous Solution Using Lemon Peel - Fe₃O₄ Nanocomposite Adsorbent. *Wasit Journal of Engineering Sciences*. 2023;11(2):94-105.
17. Sharma S, Sharma G, Kumar A, AlGarni TS, Naushad M, Alothman ZA, et al. Adsorption of cationic dyes onto carrageenan and itaconic acid-based superabsorbent

- hydrogel: Synthesis, characterization and isotherm analysis. *J Hazard Mater.* 2022;421:126729.
18. Thakur S, Chaudhary J, Thakur A, Gunduz O, Alsanie WF, Makatsoris C, et al. Highly efficient poly(acrylic acid-co-aniline) grafted itaconic acid hydrogel: Application in water retention and adsorption of rhodamine B dye for a sustainable environment. *Chemosphere.* 2022;303:134917.
 19. Saad MA, Sadik ER, Eldakiky BM, Moustafa H, Fadl E, He Z, et al. Synthesis and characterization of an innovative sodium alginate/polyvinyl alcohol bioartificial hydrogel for forward-osmosis desalination. *Sci Rep.* 2024;14(1).
 20. Abu Elella MH, Aamer N, Abdallah HM, López-Maldonado EA, Mohamed YMA, El Nazer HA, et al. Novel high-efficient adsorbent based on modified gelatin/montmorillonite nanocomposite for removal of malachite green dye. *Sci Rep.* 2024;14(1).
 21. Kamel S, El-Gendy AA, Hassan MA, El-Sakhawy M, Kelnar I. Carboxymethyl cellulose-hydrogel embedded with modified magnetite nanoparticles and porous carbon: Effective environmental adsorbent. *Carbohydr Polym.* 2020;242:116402.
 22. Malek NNA, Jawad AH, Ismail K, Razuan R, Alothman ZA. Fly ash modified magnetic chitosan-polyvinyl alcohol blend for reactive orange 16 dye removal: Adsorption parametric optimization. *Int J Biol Macromol.* 2021;189:464-476.
 23. Altam AA, Zhu L, Huang W, Huang H, Yang S. Polyelectrolyte complex beads of carboxymethylcellulose and chitosan: The controlled formation and improved properties. *Carbohydrate Polymer Technologies and Applications.* 2021;2:100100.
 24. Doondani P, Jugade R, Gomase V, Shekhawat A, Bambal A, Pandey S. Chitosan/Graphite/Polyvinyl Alcohol Magnetic Hydrogel Microspheres for Decontamination of Reactive Orange 16 Dye. *Water.* 2022;14(21):3411.
 25. Li B, Yin H. Excellent biosorption performance of novel alginate-based hydrogel beads crosslinked by lanthanum(III) for anionic azo-dyes from water. *J Dispersion Sci Technol.* 2020;42(12):1830-1842.
 26. Zhao Y, Li B. Preparation and Superstrong Adsorption of a Novel La(III)-Crosslinked Alginate/Modified Diatomite Macroparticle Composite for Anionic Dyes Removal from Aqueous Solutions. *Gels.* 2022;8(12):810.
 27. Chkirida S, Zari N, Achour R, Hassoune H, Lachehab A, Qaiss Aek, et al. Highly synergic adsorption/photocatalytic efficiency of Alginate/Bentonite impregnated TiO₂ beads for wastewater treatment. *J Photochem Photobiol A: Chem.* 2021;412:113215.
 28. El Shafey AM, Abdel-Latif MK, El-Salam HMA. The facile synthesis of poly(acrylate/acrylamide) titanium dioxide nanocomposite for groundwater ammonia removal. *Desalination and Water Treatment.* 2021;212:61-70.
 29. Alkaim AF, Abdulrazzak FH, Essa SM, Altamari US, Ramadan MF, Aljeboree AM. Methacrylic Acid-Acrylamide based ZnO Hydrogel Nanocomposite Assisted Photocatalytic Decolorization of Methylene Blue Dye. *International Journal of Pharmaceutical Quality Assurance.* 2023;14(02):279-282.
 30. Hashim FS, Alkaim AF, Mahdi SM, Omran Alkhayatt AH. Photocatalytic degradation of GRL dye from aqueous solutions in the presence of ZnO/Fe₂O₃ nanocomposites. *Composites Communications.* 2019;16:111-116.
 31. Sheikh N, Jalili L, Anvari F. A study on the swelling behavior of poly(acrylic acid) hydrogels obtained by electron beam crosslinking. *Radiat Phys Chem.* 2010;79(6):735-739.
 32. Karam FF, Hussein FH, Baqir SJ, Halbus AF, Dillert R, Bahnemann D. Photocatalytic Degradation of Anthracene in Closed System Reactor. *International Journal of Photoenergy.* 2014;2014:1-6.
 33. Thakur S, Arotiba O. Synthesis, characterization and adsorption studies of an acrylic acid-grafted sodium alginate-based TiO₂ hydrogel nanocomposite. *Adsorption Science and Technology.* 2017;36(1-2):458-477.
 34. Mhammed Alzayd AA, Radia ND. A Novel Eco-friendly Bionanocomposite: Synthesis, Optimizing Grafting Factors, Characterization, Adsorption of Ofloxacin Hydrochloride, Reinforcement Elimination System to Pharmaceutical Contaminants. *Journal of Polymers and the Environment.* 2023;32(4):1821-1836.
 35. Electrospun Poly(acrylic acid)/Silica Hydrogel Nanofibers Scaffold for Highly Efficient Adsorption of Lanthanide Ions and Its Photoluminescence Performance. *American Chemical Society (ACS).*
 36. Shi X, Wang W, Kang Y, Wang A. Enhanced swelling properties of a novel sodium alginate-based superabsorbent composites: NaAlg-g-poly(NaA-co-St)/APT. *J Appl Polym Sci.* 2012;125(3):1822-1832.